

MUMETALL

solid material

COMPOSITION (in wt%)

77 Ni – 4.5 Cu – 3.3 Mo – bal. Fe
IEC 60404-8-6 E11
DIN 17405 (1979) RNi2 / RNi5

PRODUCT DESCRIPTION

As one of the most prominent 80 % NiFe alloys, MUMETALL® stands for an exceptionally high maximum magnetic permeability paired with a very low coercivity, making it the standard material for many different kinds of application.

MAIN PROPERTIES

- Saturation polarization $J_s = 0.78$ T
- Maximum permeability $\mu_{max} = 500,000$
- Low coercivity $H_C = 0.6$ A/m



TYPICAL APPLICATIONS


High sensitivity current sensors, magnetic lenses/charged partical guiding, magnetic shielding

FORMS OF SUPPLY

- Solid rods, diameters 12.5 – 182 mm
- Solid rods, diameters ≤ 13.5 mm

Other diameters, square profile material and tolerances upon request.

For strip material, see brochure MUMETALL strip material.

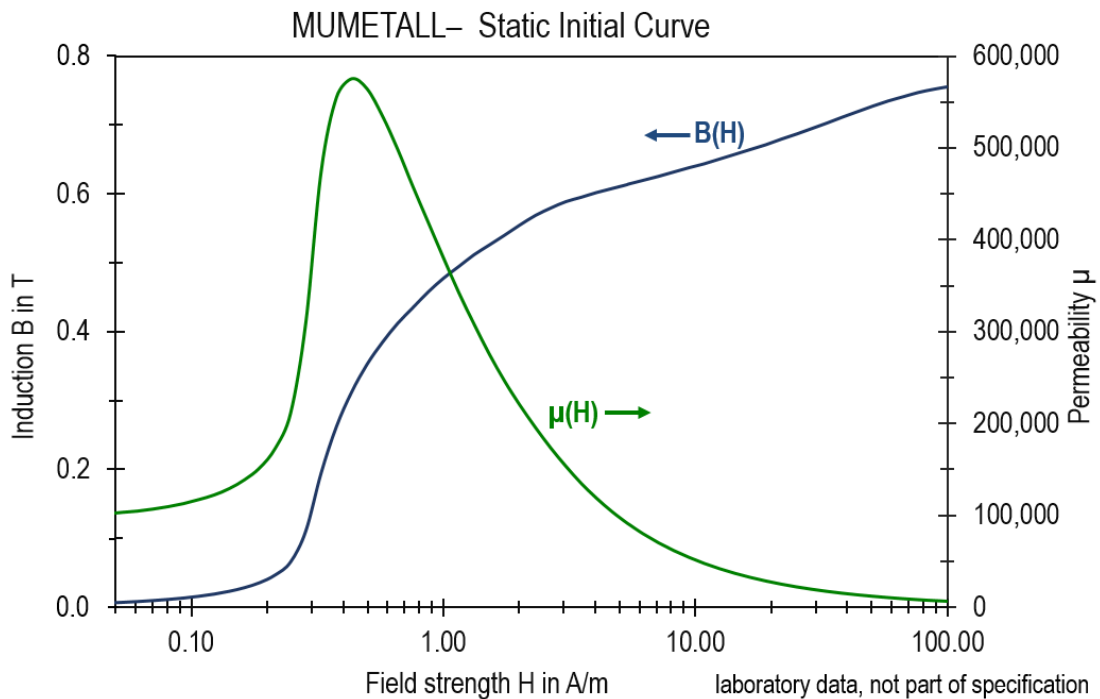

SOLID MATERIAL – TYPICAL VALUES

PHYSICAL PROPERTIES	Unit	
Mass density ρ	g/cm ³	8.7
Thermal conductivity (25 °C) λ	W/(m·K)	18 – 20
Thermal expansion coefficient (20 – 100 °C) α	10 ⁻⁶ /K	13.5
Electrical resistivity ρ_e	$\mu\Omega\text{m}$	0.6

STATIC MAGNETIC PROPERTIES

Coercivity H_c	A/m	0.6
Saturation polarization J_s	T	0.78
Saturation magnetization B_s at $H = 40$ kA/m	T	0.83
Maximum permeability μ_{max}		500,000
Initial permeability $\mu_{0.1 \text{ A/m}}$		45,000
Magnetostriction constant λ_s	ppm	~ 1
Curie temperature T_c	°C	400

MECHANICAL PROPERTIES (after recommended heat treatment)

Young's modulus E	GPa	190
Yield strength $R_{p0.2}$	MPa	150
Hardness	HV	105

MECHANICAL PROPERTIES (hot rolled)

Yield strength $R_{p0.2}$	MPa	300
Tensile strength R_m	MPa	650
Elongation A	%	> 30
Hardness	HV	160

RECOMMENDED PARAMETERS FOR HEAT TREATMENT

Atmosphere		hydrogen
Temperature	°C	1,050 – 1,150
Annealing time	h	5
Cooling rate	K/h	50 – 300

Published by VACUUMSCHMELZE GmbH & Co. KG, Hanau, March 2024
 © VACUUMSCHMELZE GmbH & Co. KG 2023. All rights reserved.
 ® is a Registered Trademark of VACUUMSCHMELZE GmbH & Co. KG